



TEST REPORT



AB-0505-T

72232750157

10-23

LAB LOCATION: TURKEY
LAB NO.: (7223)275-0157
SERVICE TYPE: Regular
DATE IN: October 03, 2023
DATE OUT: October 10, 2023

MATERIAL SUBMITTED : TC TİCARET BAKANLIĞI İSTANBUL GÜMRÜK VE DIŞ
TİCARET BÖLGE MÜDÜRLÜĞÜ İSTANBUL ÜRÜN
GÜVENLİĞİ DENETİMLERİ MÜDÜRLÜĞÜ-1 (Avrupa)
(Attn: Mustafa BİSKİN)

IMPORTER COMPANY : BIGPOINT KIRTASIYE SANAYI VE TİCARET LTD. STI.
MODEL NO : BP741-18
COVER LETTER NO : E-98552271-554.01.01-00089495303
SAMPLE RECORD NO : /
APPLICATION NO : A25256421
SUPPLIER REFERENCE : /
TESTED AGE GRADE : Over 36 M
LABELLED AGE GRADE : Over 36 M
APPLIED AGE GRADE : /
SAMPLE DESCRIPTION : **Sample A: TOY**
BRAND of SAMPLES : /
SUBMITTED CARE : /
INSTRUCTION : /
GENERAL CONCLUSION : **PASS**

C/N GK/GGY

BV CPS Test Laboratuvarları Ltd. Sti. accredited by TÜRKAK under registration number AB-0505-T for TS EN ISO/IEC 17025:2017 as test laboratory. Turkish Accreditation Agency (TURKAK) is a signatory to the European co-operation for Accreditation (EA) Multilateral Agreement (MLA) and to the International Laboratory Accreditation Cooperation (ILAC) Mutual Recognition Arrangement (MRA) for the recognition of test reports.

BV CPS TEST LABORATUVARLARI LTD. STI.
BUREAU VERITAS CONSUMER PRODUCTS SERVICES
Yalcin Kores Cad. No:22 Erdinc Binalari
A Blok 1.Kule 1.Kat 34209 Gunesli, Istanbul / Turkey
Tel:+90.212.494 35 35 Fax:+90.212.494 35 60
email:info.turkey@bvcp.com.tr
website: www.bureauveritas.com/cps

This report is governed by, and incorporates by reference, the Conditions of Testing as posted at the date of issuance of this report at <http://www.bureauveritas.com/home/about-us/our-business/cps/about-us/terms-conditions/> and is intended for your exclusive use. Any copying or replication of this report to or for any other person or entity, or use of our name or trademark, is permitted only with our prior written permission. This report sets forth our findings solely with respect to the test samples identified herein. The results set forth in this report are not indicative or representative of the quality or characteristics of the lot from which a test sample was taken or any similar or identical product unless specifically and expressly noted. Our report includes all of the tests requested by you and the results thereof based upon the information that you provided to us. Measurement uncertainty is only provided upon request for accredited tests. Statements of conformity are based on simple acceptance criteria without taking measurement uncertainty into account, unless otherwise requested in writing. You have 60 days from the date of issuance of this report to notify us of any material error or omission caused by our negligence or if you require measurement uncertainty, provided, however, that such notice shall be in writing and shall specifically address the issue you wish to raise. A failure to raise such issue within the prescribed time shall constitute your unqualified acceptance of the completeness of this report, the tests conducted and the correctness of the report contents. Testing reports without signature are not valid. BV CPS Test Laboratories is not responsible for deviations for the accuracy of the information provided by the customer that may affect the validity of the test results. Test results given in this test report represent only the sample(s) delivered to the laboratory, as sent to BV CPS Test Laboratories by the client/vendor via courier, cargo and/or manual delivery. No sampling is performed by BV CPS Test Laboratories.

SUMMARY OF TEST RESULTS

TEST PERFORMED	PASS	FAIL
EN 71-1: 2014 + A1:2018 Physical and Mechanical Properties* (See Remark for Accreditation Scope)	X	
EN 71-2: 2020 Flammability*	X	
EN 71-3:2019 + A1:2021 Migration of Certain Elements*	X	
EN 71-3:2019 + A1:2021 Migration of Certain Elements Chromium III and Chromium VI Confirmation*	X	
Polycyclic Aromatic Hydrocarbons (PAHs)*	X	
Phthalates*	X	
* TURKAK Accredited- See Appendix A		

*= The reported expanded uncertainty is based on the standard uncertainty multiplied by a coverage factor of k=2, providing a level of confidence of approximately 95%. Unless otherwise is specified, the uncertainty of measurement has not been taken into account when assessing pass/fail of the sample against the requirements of the standard. In case consideration of measurement uncertainties when assessing pass/ fail limits, some results may be in borderline. Information on uncertainty is contained in appendix A on this report.

REMARK:

I. If there are questions or concerns on this report, please contact:


+90 212 494 35 35

gaye.yildiz@bureauveritas.com

**Bureau Veritas Consumer Products Services Turkey
BV CPS Test Lab. Ltd. Sti.**




Gaye Gizem Yıldız
Asst. Client Team Lead



Hasan Altıngül
Operation Manager - CS & Support

-Photos of the Submitted Sample-

Sample A

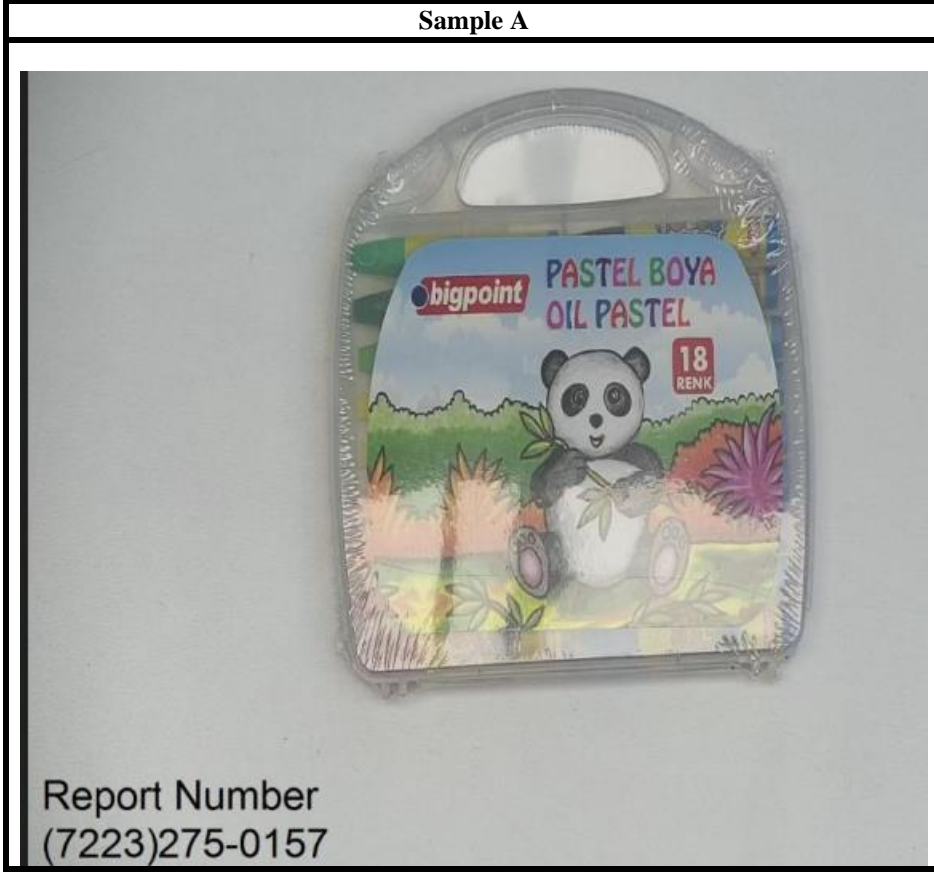

TEST RESULT

EN 71-1: 2014 + A1:2018 PHYSICAL AND MECHANICAL PROPERTIES OF TOYS

Clause	Clause Description	Test Method	RESULT
4	General Requirements	-	Sample A
4.1	Material Cleanliness	-	Pass
4.7 & 7.6	Edges	8.11	Pass
4.8 & 7.6	Points And Metallic Wires	8.12, 8.13	Pass
4.8e	Splinters	8.12, 8.13	Pass
	WARNINGS, INSTRUCTIONS FOR USE		
7	Ce Mark	-	Present
7	Manufacturer/ Importer Name And Address		Present
7	Product Identification	-	Present
7.1	General	-	Present
7.2	Toys Not Intended For Children Under 36 Months	-	Present

Remark: The methods and clauses indicated with sign “#” are not at the scope of ISO 17025 accreditation.

TEST RESULT

EN 71-2:2020 FLAMMABILITY OF TOYS

Clause	Clause Description	RESULT Sample A
4.1	General Requirements	Pass

Remark: Flammable Gases and Liquids samples which have over 15 ml volume are not at the scope of ISO 17025 accreditation

SAMPLE DESCRIPTION ASSIGNED BY LABORATORY:

Test Item	Sample Description
I001	TRANSPARENT PLASTIC
I002	RED CRAYON
I003	BORDEUX CRAYON
I004	ORANGE CRAYON
I005	NUDE CRAYON
I006	NEON YELLOW CRAYON
I007	LIGHT GREEN CRAYON
I008	KHAKI GREEN CRAYON
I009	GREEN CRAYON
I010	BLUE CRAYON
I011	DARK BLUE CRAYON
I012	PINK CRAYON
I013	PURPLE CRAYON
I014	NAVY CRAYON
I015	BROWN CRAYON
I016	DARK BROWN CRAYON
I017	GREY CRAYON
I018	BLACK CRAYON
I019	BLUE PRINT ON BOX
I020	RED PRINT ON BOX
I021	MULTICOLOR PRINT ON BOX
I022	PANDA PRINT BOX
I023	BLUE PRINT ON BOX PRINT
I024	GREEN PRINT ON BOX
I025	PINK PRINT ON BOX
I026	YELLOW BROWN GREEN PRINT ON BOX
I027	ORANGE PRINT ON BOX
I028	NAVY AND WHITE INFORMATION STICKER BACK
I029	BLACK STICKER PRINT BACK
I030	BLACK WHITE INFORMATION STICKER BACK
I031	CLOSED PLASTIC
I032	ANIMAL STICKER
I033	YELLOW PAPER ON CRAYON
I034	COLOR OIL PASTEL PRINT ON CRAYON
I035	BIG POINT PRINT ON CRAYON
I036	YELLOW CRAYON
I037	MULTICOLORED YELLOW PAPER ON CRAYON
I038	MULTICOLORED STICKER BACK AND FRONT

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result				
			I001	I002	I004	I005	I007
Type	-	I	I	I	I	I	I
Parameter	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	2250	ND	ND	2.73	ND	2.33
Antimony (Sb)	mg/kg	45	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	3.8	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	1500	ND	ND	5.06	ND	ND
Boron (B)	mg/kg	1200	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	1.3	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	37.5	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.02	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	10.5	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	622.5	2.23	ND	ND	ND	ND
Lead (Pb)	mg/kg	2.0	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	1200	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	7.5	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	75	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	37.5	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	4500	ND	ND	3.54	ND	2.44
Tin (Sn)	mg/kg	15000	ND	ND	ND	ND	ND
Organic tin	mg/kg	0.9	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	3750	ND	ND	ND	ND	ND
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected
 mg/kg = milligram(s) per kilogram
 10 000 mg/kg = 1 %
 Detection Limit (mg/kg) :
 For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ; Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2
 For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

“>” = Greater than
 mg/kg = ppm = part(s) per million
 % = percent

Conc. = Concentration
 mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result				
			I008	I009	I010	I011	I012
Type	-	I	I	I	I	I	I
Parameter	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	2250	2.67	ND	3.24	ND	3.62
Antimony (Sb)	mg/kg	45	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	3.8	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	1500	ND	ND	ND	ND	2.26
Boron (B)	mg/kg	1200	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	1.3	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	37.5	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.02	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	10.5	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	622.5	ND	ND	ND	ND	ND
Lead (Pb)	mg/kg	2.0	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	1200	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	7.5	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	75	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	37.5	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	4500	2.80	2.06	3.68	ND	3.66
Tin (Sn)	mg/kg	15000	ND	ND	ND	ND	ND
Organic tin	mg/kg	0.9	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	3750	ND	ND	ND	ND	ND
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected
 mg/kg = milligram(s) per kilogram
 10 000 mg/kg = 1 %
 Detection Limit (mg/kg) :
 For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ; Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2
 For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

“>” = Greater than
 mg/kg = ppm = part(s) per million
 % = percent

Conc. = Concentration
 mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result					
			I013	I014	I015	I016	I017	I018
Type	-	I	I	I	I	I	I	I
Parameter	-	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	2250	2.21	61.34	2.35	ND	ND	4.69
Antimony (Sb)	mg/kg	45	ND	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	3.8	ND	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	1500	ND	ND	ND	ND	ND	ND
Boron (B)	mg/kg	1200	ND	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	1.3	ND	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	37.5	ND	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.02	ND	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	10.5	ND	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	622.5	ND	ND	ND	ND	ND	ND
Lead (Pb)	mg/kg	2.0	ND	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	1200	ND	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	7.5	ND	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	75	ND	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	37.5	ND	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	4500	3.25	2.85	ND	ND	ND	3.93
Tin (Sn)	mg/kg	15000	ND	ND	ND	ND	ND	ND
Organic tin	mg/kg	0.9	ND	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	3750	ND	ND	ND	ND	ND	ND
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected

mg/kg = milligram(s) per kilogram

10 000 mg/kg = 1 %

Detection Limit (mg/kg) :

For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;

Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2

For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

">" = Greater than

mg/kg = ppm = part(s) per million

% = percent

Conc. = Concentration

mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result	
			I003	I006
Type	-	I	I	I
Parameter	-	-	-	-
Aluminium (Al)	mg/kg	2250	4.44	3.47
Antimony (Sb)	mg/kg	45	ND	ND
Arsenic (As)	mg/kg	3.8	ND	ND
Barium (Ba)	mg/kg	1500	10.76	ND
Boron (B)	mg/kg	1200	ND	ND
Cadmium (Cd)	mg/kg	1.3	ND	ND
Chromium III (Cr III)	mg/kg	37.5	0.05	0.06
Chromium VI (Cr VI)	mg/kg	0.02	ND	ND
Cobalt (Co)	mg/kg	10.5	ND	ND
Copper (Cu)	mg/kg	622.5	ND	ND
Lead (Pb)	mg/kg	2.0	ND	ND
Manganese (Mn)	mg/kg	1200	ND	ND
Mercury (Hg)	mg/kg	7.5	ND	ND
Nickel (Ni)	mg/kg	75	ND	ND
Selenium (Se)	mg/kg	37.5	ND	ND
Strontium (Sr)	mg/kg	4500	3.92	2.84
Tin (Sn)	mg/kg	15000	ND	ND
Organic tin	mg/kg	0.9	ND	ND
Zinc (Zn)	mg/kg	3750	2.59	ND
Conclusion	-	-	PASS	PASS

Note:

ND = Not detected “>” = Greater than Conc. = Concentration
mg/kg = milligram(s) per kilogram mg/kg = ppm = part(s) per million
10 000 mg/kg = 1 % % = percent mcg/sq. m = microgram per square metre
Detection Limit (mg/kg) :
For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;
Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2
For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ;
Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result				
			I019	I020	I022	I023	I024
Type	-	III	III	III	III	III	III
Parameter	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	28130	91.84	29.75	79.75	84.28	79.03
Antimony (Sb)	mg/kg	560	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	47	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	18750	ND	ND	ND	ND	ND
Boron (B)	mg/kg	15000	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	17	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	460	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.053	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	130	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	7700	ND	ND	ND	ND	ND
Lead (Pb)	mg/kg	23	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	15000	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	94	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	930	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	460	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	56000	2.16	ND	2.52	2.84	2.71
Tin (Sn)	mg/kg	180000	ND	ND	ND	ND	ND
Organic tin	mg/kg	12	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	46000	ND	9.11	ND	ND	ND
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected

">" = Greater than

Conc. = Concentration

mg/kg = milligram(s) per kilogram

mg/kg = ppm = part(s) per million

10 000 mg/kg = 1 %

% = percent

mcg/sq. m = microgram per square metre

Detection Limit (mg/kg) :

For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;

Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2

For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ;

Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result				
			I025	I026	I027	I028	I029
Type	-	III	III	III	III	III	III
Parameter	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	28130	73.77	75.68	69.47	65.84	44.94
Antimony (Sb)	mg/kg	560	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	47	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	18750	ND	ND	ND	ND	ND
Boron (B)	mg/kg	15000	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	17	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	460	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.053	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	130	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	7700	ND	ND	ND	ND	ND
Lead (Pb)	mg/kg	23	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	15000	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	94	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	930	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	460	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	56000	2.57	2.88	2.49	2.27	2.10
Tin (Sn)	mg/kg	180000	ND	ND	ND	ND	ND
Organic tin	mg/kg	12	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	46000	ND	ND	ND	ND	2.45
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected

mg/kg = milligram(s) per kilogram

10 000 mg/kg = 1 %

Detection Limit (mg/kg) :

For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;

Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2

For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

“>” = Greater than

mg/kg = ppm = part(s) per million

% = percent

Conc. = Concentration

mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result				
			I030	I031	I032	I033	I034
Type	-	III	III	III	III	III	III
Parameter	-	-	-	-	-	-	-
Aluminium (Al)	mg/kg	28130	23.81	ND	81.05	13.57	13.53
Antimony (Sb)	mg/kg	560	ND	ND	ND	ND	ND
Arsenic (As)	mg/kg	47	ND	ND	ND	ND	ND
Barium (Ba)	mg/kg	18750	ND	ND	ND	ND	ND
Boron (B)	mg/kg	15000	ND	ND	ND	ND	ND
Cadmium (Cd)	mg/kg	17	ND	ND	ND	ND	ND
Chromium III (Cr III)	mg/kg	460	ND	ND	ND	ND	ND
Chromium VI (Cr VI)	mg/kg	0.053	ND	ND	ND	ND	ND
Cobalt (Co)	mg/kg	130	ND	ND	ND	ND	ND
Copper (Cu)	mg/kg	7700	ND	ND	ND	ND	ND
Lead (Pb)	mg/kg	23	ND	ND	ND	ND	ND
Manganese (Mn)	mg/kg	15000	ND	ND	ND	ND	ND
Mercury (Hg)	mg/kg	94	ND	ND	ND	ND	ND
Nickel (Ni)	mg/kg	930	ND	ND	ND	ND	ND
Selenium (Se)	mg/kg	460	ND	ND	ND	ND	ND
Strontium (Sr)	mg/kg	56000	ND	ND	2.36	7.47	7.27
Tin (Sn)	mg/kg	180000	ND	ND	ND	ND	ND
Organic tin	mg/kg	12	ND	ND	ND	ND	ND
Zinc (Zn)	mg/kg	46000	ND	ND	ND	ND	ND
Conclusion	-	-	PASS	PASS	PASS	PASS	PASS

Note:

ND = Not detected

mg/kg = milligram(s) per kilogram

10 000 mg/kg = 1 %

Detection Limit (mg/kg) :

For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;

Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2

For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

">" = Greater than

mg/kg = ppm = part(s) per million

% = percent

Conc. = Concentration

mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

Test Item(s)	Unit	Req.	Result	
			I035	I036
Type	-	III	III	III
Parameter	-	-	-	-
Aluminium (Al)	mg/kg	28130	13.75	2.81
Antimony (Sb)	mg/kg	560	ND	ND
Arsenic (As)	mg/kg	47	ND	ND
Barium (Ba)	mg/kg	18750	ND	ND
Boron (B)	mg/kg	15000	ND	ND
Cadmium (Cd)	mg/kg	17	ND	ND
Chromium III (Cr III)	mg/kg	460	ND	ND
Chromium VI (Cr VI)	mg/kg	0.053	ND	ND
Cobalt (Co)	mg/kg	130	ND	ND
Copper (Cu)	mg/kg	7700	ND	ND
Lead (Pb)	mg/kg	23	ND	ND
Manganese (Mn)	mg/kg	15000	ND	ND
Mercury (Hg)	mg/kg	94	ND	ND
Nickel (Ni)	mg/kg	930	ND	ND
Selenium (Se)	mg/kg	460	ND	ND
Strontium (Sr)	mg/kg	56000	7.59	3.53
Tin (Sn)	mg/kg	180000	ND	ND
Organic tin	mg/kg	12	ND	ND
Zinc (Zn)	mg/kg	46000	ND	ND
Conclusion	-	-	PASS	PASS

Note:

ND = Not detected
 mg/kg = milligram(s) per kilogram
 10 000 mg/kg = 1 %
 Detection Limit (mg/kg) :
 For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ; Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2
 For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ; Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

">" = Greater than
 mg/kg = ppm = part(s) per million
 % = percent

Conc. = Concentration
 mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS

Test Method : European Standard EN 71-3:2019+A1:2021

See Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

	Unit	Req.	Result
Test Item(s)	-	-	I021
Type	-	III	III
Parameter	-	-	-
Aluminium (Al)	mg/kg	28130	215.51
Antimony (Sb)	mg/kg	560	ND
Arsenic (As)	mg/kg	47	ND
Barium (Ba)	mg/kg	18750	2.64
Boron (B)	mg/kg	15000	ND
Cadmium (Cd)	mg/kg	17	ND
Chromium III (Cr III)	mg/kg	460	0.12
Chromium VI (Cr VI)	mg/kg	0.053	ND
Cobalt (Co)	mg/kg	130	ND
Copper (Cu)	mg/kg	7700	ND
Lead (Pb)	mg/kg	23	ND
Manganese (Mn)	mg/kg	15000	2.54
Mercury (Hg)	mg/kg	94	ND
Nickel (Ni)	mg/kg	930	ND
Selenium (Se)	mg/kg	460	ND
Strontium (Sr)	mg/kg	56000	7.87
Tin (Sn)	mg/kg	180000	ND
Organic tin	mg/kg	12	ND
Zinc (Zn)	mg/kg	46000	31.86
Conclusion	-	-	PASS

Note:

ND = Not detected “>” = Greater than Conc. = Concentration
mg/kg = milligram(s) per kilogram mg/kg = ppm = part(s) per million
10 000 mg/kg = 1 % % = percent mcg/sq. m = microgram per square metre
Detection Limit (mg/kg) :
For Type I and Type II - Al : 2 ; Sb : 2 ; As : 0.15 ; Ba : 2 ; B : 2 ; Cd : 0.15 ; Cr III : 0.15 ; Cr VI : 0.005 [0.002] ;
Co : 2 ; Cu : 2 ; Pb : 0.5 ; Mn : 2 ;
Hg : 0.15 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 0.04 ; Zn : 2
For Type III - Al : 2 ; Sb : 2 ; As : 2 ; Ba : 2 ; B : 2 ; Cd : 2 ; Cr III : 0.15 ; Cr VI : 0.05 [0.002] ; Co : 2 ; Cu : 2 ;
Pb : 2 ; Mn : 2 ; Hg : 2 ; Ni : 2 ; Se : 2 ; Sr : 2 ; Sn : 2 ; Organic tin : 2 ; Zn : 2

Remark:

TEST RESULT

EN 71-3:2019 + A1:2021 MIGRATION OF CERTAIN ELEMENTS CHROMIUM III AND CHROMIUM VI CONFIRMATION

Test Method : European Standard EN 71-3:2019+A1:2021

Se Soluble Element (Parameter) and its corresponding Maximum Allowable Limit (Req.) in Result Table	Type I	Dry, brittle, powder-like or pliable toy material
	Type II	Liquid or sticky toy material
	Type III	Scraped-off toy material

	Unit	Req.	Result	
Test Item(s)	-	-	I003	I006
Type	-	I	I	I
Parameter	-	-	-	-
Chromium VI (Cr VI)	mg/kg	0.002	ND	ND
Conclusion	-	-	PASS	PASS

	Unit	Req.	Result	
Test Item(s)	-	-	I021	
Type	-	III	III	
Parameter	-	-	-	
Chromium VI (Cr VI)	mg/kg	0.053	ND	
Conclusion	-	-	PASS	

Note:

ND = Not detected
 mg/kg = milligram(s) per kilogram
 10 000 mg/kg = 1 %
 Detection Limit (mg/kg) :
 For Type I and Type II - Cr VI : 0.005 [0.002]
 For Type III - Cr VI : 0.05 [0.002]

“>” = Greater than
 mg/kg = ppm = part(s) per million
 % = percent

Conc. = Concentration
 mcg/sq. m = microgram per square metre

Remark:

TEST RESULT

POLYCYCLIC AROMATIC HYDROCARBONS (PAHS)

Test Method : All materials: AFPS GS 2019
Quantification analysis by GC-MS

Maximum Limit:	Each of 8 PAHs < 0.5 mg/kg
-----------------------	--------------------------------------

Tested Item(s)	Result			Conclusion
	Detected Analyte(s)	Conc.	Unit	
I001+I002+I003	/	ND	mg/kg	PASS
I004+I005+I006	/	ND	mg/kg	PASS
I007+I008+I009	/	ND	mg/kg	PASS
I010+I011+I012	/	ND	mg/kg	PASS
I013+I014+I015	/	ND	mg/kg	PASS
I016+I017+I018	/	ND	mg/kg	PASS
I037+I038	/	ND	mg/kg	PASS

ND = Not detected
mg/kg = milligram(s) per kilogram
10 000 mg/kg = 1 %
Detection Limit (mg/kg) - 0.1 each

“>” = Greater than
mg/kg = ppm = part(s) per million
% = percent

Conc. = Concentration

Remark:

- The list of Polycyclic Aromatic Hydrocarbons (PAHs) is summarized in table of Appendix.

TEST RESULT

PHTHALATES

Test Method : CPSC-CH-C1001-09.3
Quantification analysis by GC-MS or LC-DAD-MS

Maximum Limit:	Sum of (DBP, BBP, DEHP): Less than 1000 mg/kg Sum of (DNOP, DIDP, DINP): Less than 1000 mg/kg			
Tested Item(s)	Result			Conclusion
	Detected Analyte(s)	Conc.	Unit	
I001+I002+I003	/	ND	mg/kg	PASS
I004+I005+I006	/	ND	mg/kg	PASS
I007+I008+I009	/	ND	mg/kg	PASS
I010+I011+I012	/	ND	mg/kg	PASS
I013+I014+I015	/	ND	mg/kg	PASS
I016+I017+I018	/	ND	mg/kg	PASS
I037+I038	/	ND	mg/kg	PASS

Note:

ND = Not detected
mg/kg = milligram(s) per kilogram
10 000 mg/kg = 1 %
Detection Limit (mg/kg) - 50 each

“>” = Greater than
mg/kg = ppm = part(s) per million
% = percent

Conc. = Concentration

Remark:

- The list of Phthalates is summarized in table of Appendix.

APPENDIX A –LIST OF MEASUREMENT UNCERTAINTIES		
TEST NAME	STANDARD NAME	MEASUREMENT UNCERTAINTY
Migration Of Certain Elements	European Standard EN 71 Part 3: 2019, Section 8.	± % 26,78
Phthalates	CPSC-CH-C1001-09.03	± %16,53
Polycyclic Aromatic Hydrocarbons (PAHs)	AFPS GS 2019	± % 19.44

APPENDIX

List of Phthalates:

No.	Name of Analytes	CAS-No.	No.	Name of Analytes	CAS-No.
1	Butylbenzylphthalate (BBP)	85-68-7	4	Di-n-octylphthalate (DNOP)	117-84-0
2	Dibutylphthalate (DBP)	84-74-2	5	Di-iso-nonylphthalate (DINP)	28553-12-0
3	Di(2-ethylhexyl)-phthalate (DEHP)	117-81-7	6	Diisodecylphthalate (DIDP)	26761-40-0

List of Polycyclic Aromatic Hydrocarbons (PAHs):

No.	Name of Analytes	CAS-No.	No.	Name of Analytes	CAS-No.
1	Benzo (a) anthracene	56-55-3	5	Dibenzo (a,h) anthracene	53-70-3
2	Chrysene	218-01-9	6	Benzo (b) fluoranthene	205-99-2
3	Benzo (a) pyrene	50-32-8	7	Benzo (k) fluoranthene	207-08-9
4	Benzo (e) pyrene	192-97-2	8	Benzo (j) fluoranthene	205-82-3

-END OF REPORT-